

# Self Assembly and Properties of C:WO<sub>3</sub> Nano-Platelets and C:VO<sub>2</sub>/V<sub>2</sub>O<sub>5</sub> Triangular Capsules Produced by Laser Solution Photolysis

B. W. Mwakikunga · A. Forbes · E. Sideras-Haddad · M. Scriba · E. Manikandan

Received: 24 October 2009 / Accepted: 11 November 2009 / Published online: 1 December 2009  
© The Author(s) 2009. This article is published with open access at Springerlink.com

**Abstract** Laser photolysis of WCl<sub>6</sub> in ethanol and a specific mixture of V<sub>2</sub>O<sub>5</sub> and VCl<sub>3</sub> in ethanol lead to carbon modified vanadium and tungsten oxides with interesting properties. The presence of graphene's aromatic rings (from the vibrational frequency of 1,600 cm<sup>-1</sup>) together with C–C bonding of carbon (from the Raman shift of 1,124 cm<sup>-1</sup>) present unique optical, vibrational, electronic and structural properties of the intended tungsten trioxide and vanadium dioxide materials. The morphology of these samples shows nano-platelets in WO<sub>x</sub> samples and, in VO<sub>x</sub> samples, encapsulated spherical quantum dots in

conjunction with fullerenes of VO<sub>x</sub>. Conductivity studies revealed that the VO<sub>2</sub>/V<sub>2</sub>O<sub>5</sub> nanostructures are more sensitive to Cl than to the presence of ethanol, whereas the C:WO<sub>3</sub> nano-platelets are more sensitive to ethanol than atomic C.

**Keywords** Carbon · VO<sub>2</sub> · V<sub>2</sub>O<sub>5</sub> · WO<sub>3</sub> · Laser · Photolysis · Sensors

## Introduction

The study of vanadium and tungsten oxides has been undertaken extensively in recent years due to their respective thermo-chromic and electro-chromic and hence gas-chromatic properties. Since the discovery of the metal-to-insulator transition (MIT) at 340 K of VO<sub>2</sub> in 1959 by Morin [1] and electro-chromism of WO<sub>3</sub> in 1975 by Faughnan [2, 3], and also due to the fact that the tungsten metal is, so far, the best known dopant in VO<sub>2</sub> to reduce the MIT temperature to room temperature, the study of the two materials together is expected to yield a good understanding of their MIT behaviours especially at the nano-scale as discussed by this group and others previously [4–6]. To date, self assembly of these materials has been achieved by a number of techniques, including: hydrothermal techniques [7], employing templates either with polymers or pre-assembled carbon nanotubes [8], CVD epitaxial growth [9], sol–gel [10], ion implantation [11], hot-wire CVD [12], sputtering [13] and ultrasonic spray pyrolysis [14–18]. Also V<sub>2</sub>O<sub>5</sub> capsules [19], WO<sub>3</sub> nano-rods and nano-wires and nano-arrays [20–22] have previously been obtained using several techniques. Laser synthesis methods have been of particular interest and have been followed by this group previously [23, 24]. The

---

B. W. Mwakikunga (✉) · A. Forbes  
CSIR National Laser Centre, P. O. Box 395, Pretoria 0001,  
South Africa  
e-mail: bmwakikunga@csir.co.za

A. Forbes  
e-mail: aforbes1@csir.co.za

B. W. Mwakikunga · E. Sideras-Haddad  
DST/NRF Centre of Excellence in Strong Materials and School  
of Physics, University of the Witwatersrand, Johannesburg,  
South Africa


B. W. Mwakikunga  
Department of Physics, University of Malawi-The Polytechnic,  
Private Bag 303, Chichiri, Blantyre 3, Malawi

E. Sideras-Haddad  
iThemba LABS, Private Bag 11, Wits 2050, Jan Smuts &  
Empire Rd., Johannesburg, South Africa

A. Forbes  
School of Physics, University of Kwazulu-Natal, Private Bag  
X54001, Durban 4000, South Africa

M. Scriba · E. Manikandan  
DST/CSIR National Centre for Nano-Structured Materials,  
P. O. Box 395, Pretoria, South Africa







When the same precursors are irradiated with the 248-nm beam from the KrF excimer laser, the  $\text{W}(\text{OR})_6$  liquid turns blue-black before stabilising to a yellow colour after a few days, whereas no colour change is seen in the vanadium precursor. It is suggested that at this wavelength, a different bond is dissociated namely the C–H bond which has a frequency of between 3,000 and 3,300  $\text{cm}^{-1}$  compared to the laser frequency of 40,322  $\text{cm}^{-1}$  (at  $\lambda = 248$  nm). The C–H bond then has a higher probability of being dissociated than the O–C bond, since the C–H bond is only 10 times lower than the laser frequency when compared to the O–C which is 40 times lower. Also, the C–H bond is capable of oscillating closer to the laser frequency via other higher order vibrational modes.

The scanning electron microscopy image of carbon modified  $\text{WO}_x$  nano-platelets presented in Fig. 1 shows significant stacking between the platelets and the formation of chains. A relatively narrow size distribution of the particles can be observed. Local EDS (inset of Fig. 1) demonstrates the purity of the carbon modified  $\text{WO}_3$  sample. A carbon shoulder peak at X-ray energy of about 0.3 keV could clearly be observed.

X-ray diffraction (XRD) results from the carbon modified  $\text{WO}_3$  nano-platelets are presented in Fig. 2. In our carbon modified  $\text{WO}_3$  sample, the usual triplet peaks at  $2\theta$  values of 23.117°, 23.583° and 24.583° corresponding to the Miller indices of (002), (020) and (200) (International

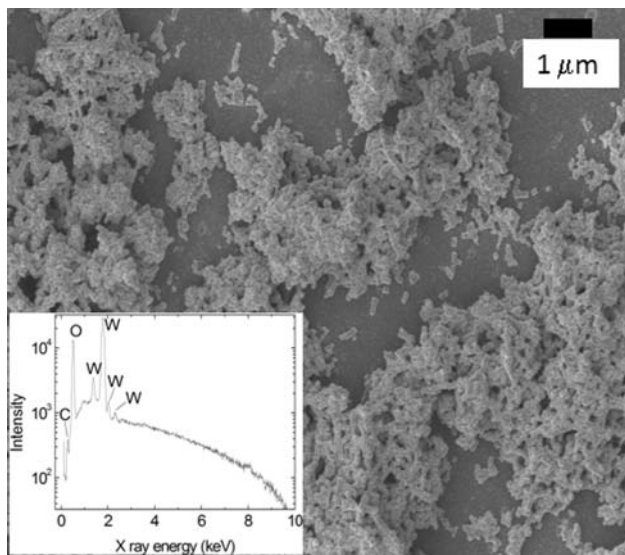

**Fig. 1** Scanning electron micrograph of the carbon modified  $\text{WO}_3$  particles produced by laser solution photolysis. The inset shows elemental composition of the sample by EDS

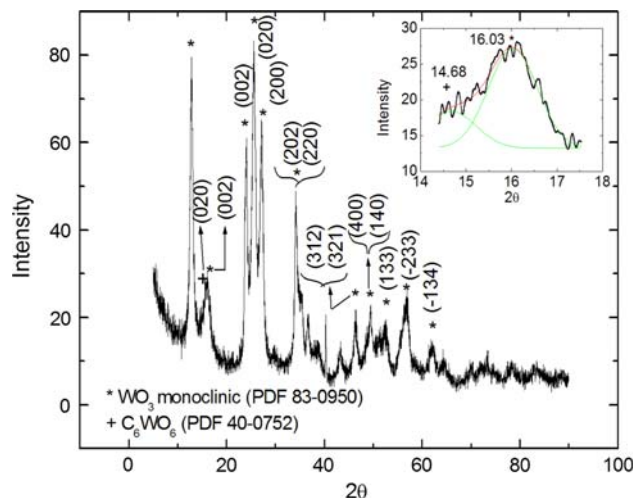

**Fig. 2** X-ray diffraction of the carbon modified  $\text{WO}_3$  nano-platelets. Note the shoulder peak at  $2\theta = 14.63^\circ$  which closely matches that of  $\text{C}_6\text{WO}_6$  at  $2\theta = 15.595^\circ$


Crystallographic Diffraction Data (ICDD) Powder Diffraction File (PDF) 83-0950) are found to be shifted to  $2\theta = 23.736^\circ$ ,  $25.463^\circ$  and  $27.325^\circ$ , respectively. This indicates that this is indeed the  $\text{WO}_3$  crystal but its structure is significantly distorted by dopants. Based on the initial reagents and EDS spectrum in the inset of Fig. 1, the dopant for  $\text{WO}_3$  nanoplates is only carbon. No hydrogen or chlorine peaks were found. From more searches in the ICDD database, the PDF No 40-0752 of  $\text{C}_6\text{WO}_6$  has a strong peak at  $2\theta = 15.595^\circ$  with the  $(hkl)$  coordinates of (002) or (101) which closely matches the shoulder peak in the present sample at  $2\theta = (14.63 \pm 0.54)^\circ$ . This peak is not found in all files of stoichiometric  $\text{WO}_3$ . This suggests that carbon is the most important dopant in this case.

The distortion of the  $\text{WO}_3$  structure observed by high resolution transmission electron microscopy (Fig. 3) supports the XRD results. The (002), (020) and (200) planes in stoichiometric  $\text{WO}_3$  (PDF 80-0950) are expected to have  $d$ -spacings of 3.8443, 3.7694 and 3.6499 Å. Based on the TEM observations of our carbon modified  $\text{WO}_3$  crystals, the inter-planar  $d$ -spacings are 4.70, 3.52 and 3.38 Å, respectively.

Our  $\text{VO}_x$  sample was also prepared similarly and observed by TEM. Triangular envelope-like structures of about 400 nm on each side of the triangle are the predominant polymorphs. The triangles are thin layers of  $\text{VO}_x$  with an interplanar spacing of 3.75 Å as shown in Fig. 4. Observed at higher magnification, the layers were found to be envelopes containing spherical nano-particles with an average size of 6 nm. These  $\text{VO}_x$  quantum dots which can be solid (multi-walled) spheres or  $\text{VO}_x$  fullerenes are found to have the same size distribution, as shown in the inset (d) of Fig. 4. An EDS spectrum of such nanostructures placed




**Fig. 3** **a** Low magnification TEM image of the  $\text{WO}_x$  showing stacking of nano-platelets, **b** cross-sectional view of one stacking, showing each platelet can be up to 20 nm thick with one preferred direction of stacking as shown by the inset of the image's FFT. **c** Top-view of two platelets stacked together showing the inter-planar spacing, angles and the two-dimensional growth shown by FFT of the image in the inset of **c**

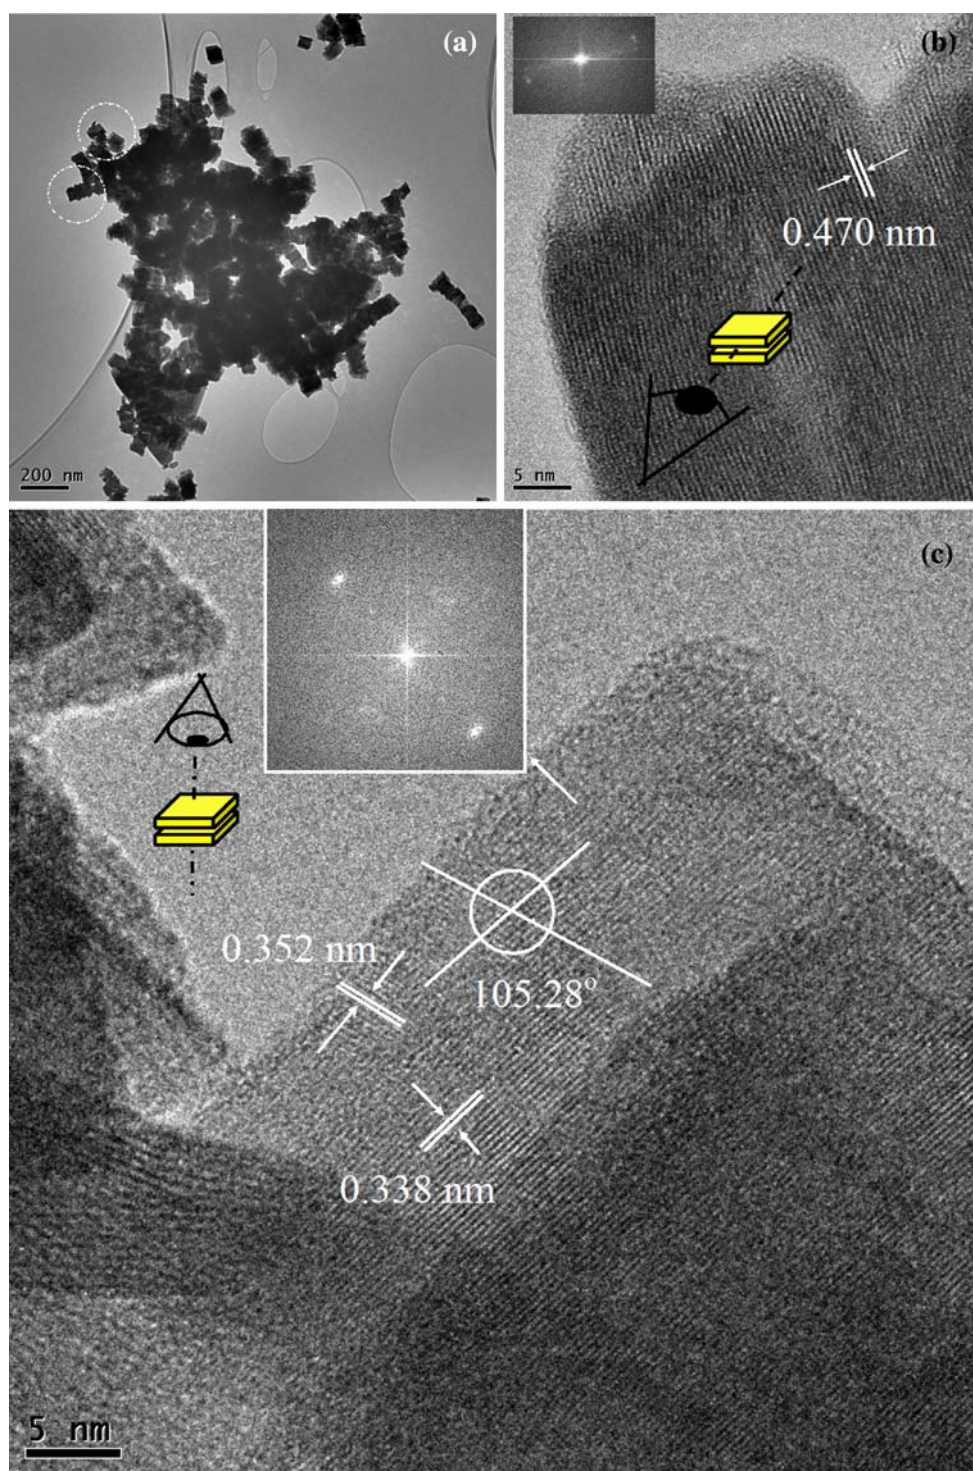

on Si(111) surface (inset (e) in Fig. 4) showed peaks for V and O alongside the major Si(111) from the substrate and trace amounts of Na, Cl and Ca. This confirms the morphology studies done by SEM of such a sample (not shown here) where the triangular capsules were interspaced by large cubic crystals presumably of NaCl and  $\text{CaCl}_2$  which have been segregated from the  $\text{V}_2\text{O}_5/\text{VO}_2$  triangular

capsules. Also, carbon doping is confirmed in the capsules by the C shoulder peak at 0.3 keV.

From Raman spectroscopy of the carbon modified  $\text{WO}_x$  shown in Fig. 5, a slight red-shift from 705 to 674  $\text{cm}^{-1}$  can be observed, corresponding to the bending modes in  $\text{WO}_3$  of O–W–O. The suppression of the stretching mode of the same bond at 800  $\text{cm}^{-1}$  is presumed to be due to the

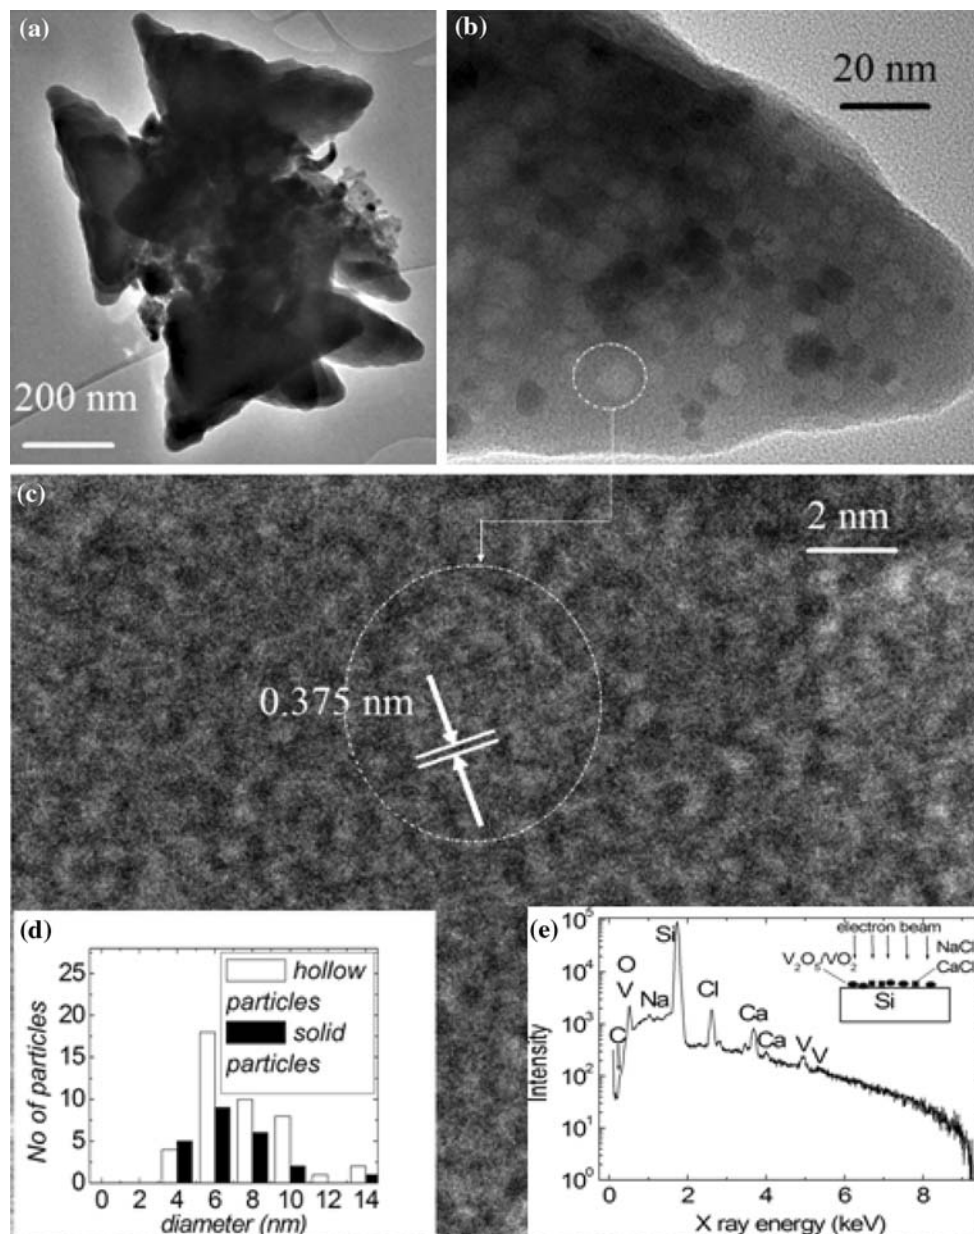

**Fig. 4** **a** Low magnification TEM of the triangular envelopes of  $\text{VO}_x$ , **b** one pocket at higher magnification, showing the small voids and solid spheres, **c** HRTEM of one of the hollow quantum dots and, **d**


size distribution histograms for the hollow and solid quantum dots of  $\text{VO}_x$  and **e** EDS of the C:  $\text{V}_2\text{O}_5/\text{VO}_2$  nanostructures showing their elemental composition

presence of the dopants. Only the surface  $\text{W}=\text{O}$  stretching mode at  $958\text{ cm}^{-1}$  is unchanged by the new structure. This peak is broadened towards the higher wave-numbers—beyond  $1,000\text{ cm}^{-1}$ . It should also be noted that the  $\text{O}-\text{C}$  bond found in ethanol, which could be the bridge between the dopant carbon and the  $\text{WO}_6$  octahedra in the  $\text{WO}_3$  structure in this case, has a vibrational frequency of  $1,000\text{ cm}^{-1}$  [34]. The presence of carbon is signified by the peak close to  $1,580\text{ cm}^{-1}$  showing aromatic rings of carbon which form the perfect graphite  $sp^2$  bonding structure. We did not find any D band at  $1,354\text{ cm}^{-1}$  in this sample

showing that there is no disorder in the aromatic network structure of the dopant C. However, there is a new sharp peak at  $1,124\text{ cm}^{-1}$  which could be assigned to  $\text{C}-\text{C}$  bond vibration, in agreement with previously observed glucose carbon vibrations at  $1,126\text{ cm}^{-1}$  [34]. Ferrari et al. [35] previously observed a peak at  $1,060\text{ cm}^{-1}$  in diamond-like-carbon and assigned this phonon frequency to  $sp^3$  bonding but this was found to be too far from the  $1,124\text{ cm}^{-1}$  peak observed presently to be acceptable.

Fourier-transform infrared spectroscopy of the carbon modified  $\text{WO}_3$  (Fig. 6) supports the results obtained by



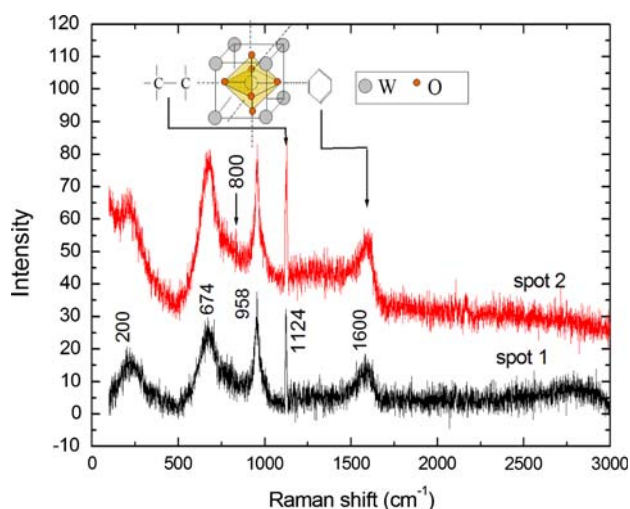


**Fig. 5** Raman spectra of the carbon modified  $\text{WO}_x$  nano-platelets showing the characteristics peaks for the crystal  $\text{WO}_3$  and those of aromatic carbon at  $1,600\text{ cm}^{-1}$ . The peak at  $1,124\text{ cm}^{-1}$  closely matches that of  $1,126\text{ cm}^{-1}$  assigned to C–C bond vibration

Raman spectroscopy. The strong and broad absorption peak at  $598\text{ cm}^{-1}$  with its shoulder at  $730\text{ cm}^{-1}$  can be assigned to the O–W–O stretching vibrations in the  $\text{WO}_3$  structure, whereas the  $916\text{ cm}^{-1}$  peak corresponds to the W=O surface stretching modes due to dangling oxygen bonds. The red-shift from the Raman allowed  $960\text{ cm}^{-1}$  to the IR allowed  $916\text{ cm}^{-1}$  could be due to the loading of carbon on these bonds. Carbon doping is confirmed by the presence of the peaks assigned to the C–O bonding at  $1,000$  and  $1,054\text{ cm}^{-1}$ ; these could not be observed in Raman spectroscopy for reasons not established yet. The  $1,600\text{ cm}^{-1}$  phonon frequency assigned to the perfect graphite's aromatic carbon ring is confirmed by FTIR as previously seen in Raman spectroscopy. The group of absorption peaks from  $3,000$  to  $3,550\text{ cm}^{-1}$  have previously been assigned to OH bonds which suggest that some terminal oxygen atoms in the  $\text{WO}_3$  structure are not only bonded to the carbon aromatic rings but also to hydrogen. No C–H bonds were found by FTIR.


### Possible Mechanism of Formation of the Triangular Envelopes and $\text{VO}_x$ Inorganic Fullerenes

Since the discovery of carbon nano-tube structure in the early 1980s, Tenne and co-workers also reported similar structures in  $\text{WSe}_2$  and  $\text{MoS}_2$  [36]. The argument was that metal chalcogenides and oxides are also capable of arranging their unit cells in a hexagonal close packing as in carbon, thereby forming a layer of atoms whose edges leave dangling bonds. These bonds cause intense attractive

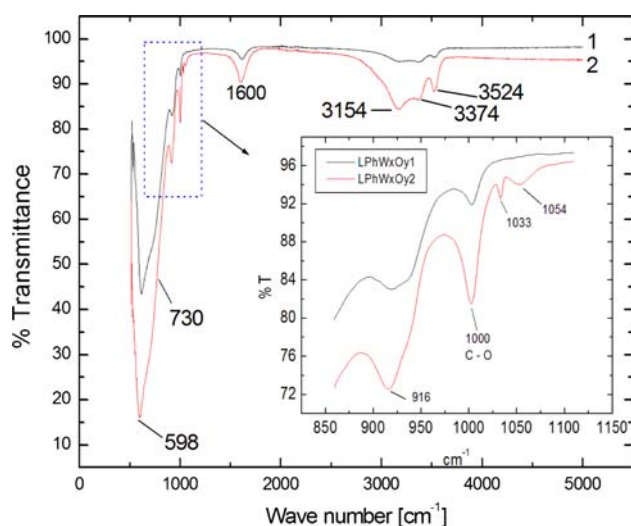


**Fig. 6** Infrared spectra of two samples of carbon-doped  $\text{WO}_3$ . Sample 2 was exposed to carbon for a longer period of time than sample 1. The carbon doping is confirmed by the existence of the carbon–oxygen bond at  $1,000$  and  $1,054\text{ cm}^{-1}$  in both samples

forces which compel the layer to fold on itself into various shapes such as tubes, scrolls and rods. Formation of fullerenes is due to defects which are found to be pentagonal, rectangular and triangular bonds, which are possible in all transition metal compounds. Different processes of formation of, for instance,  $\text{V}_2\text{O}_5$  capsules [37, 38] have led authors to suggest various mechanisms. We suggest that the formation of our triangular envelopes/capsules starts with the formation of closely packed hexagonal 2-D layers when the  $\text{VO}_x$  is subjected to the laser beam. This assumption is based on the known experimental and theoretical facts from computer modelling that  $\text{V}_2\text{O}_5$  is capable of wrapping into  $\text{V}_2\text{O}_5$  nano-tubes [39] either as a zig-zag framework or in an arm chair structure [40]. It is also known that a mixture of  $\text{V}^{4+}$  and  $\text{V}^{5+}$  in  $(\text{V}^{\text{IV}}\text{O})[\text{V}^{\text{V}}\text{O}_4]_0.5[\text{C}_3\text{N}_2\text{H}_{12}]$  can lead to a layered structure [41]. The organic layer intercalates the inorganic counterpart with the latter containing square pyramids formed by  $\text{V}^{4+}$  ions and tetrahedral pyramids formed by  $\text{V}^{5+}$  ions. On this layer are randomly scattered fullerenes of the same material which have self-assembled under the same laser beam. These fullerenes together with dangling bonds on the layer periphery exert intense attractive forces which cause the layer to fold on itself in a certain pattern. A schematic cartoon of the possible formation of the  $\text{VO}_2/\text{V}_2\text{O}_5$  triangular envelopes that encapsulate the  $\text{VO}_2/\text{V}_2\text{O}_5$  QDs and the  $\text{VO}_2/\text{V}_2\text{O}_5$  fullerenes are shown in Fig. 7. A hexagonal packing in a zig-zag fashion ends up having arm-chair structure dangling bonds in the periphery of the hexagon. The dangling bonds and the van der Waal's forces from the particles sitting on the surface compel this sheeting to wrap

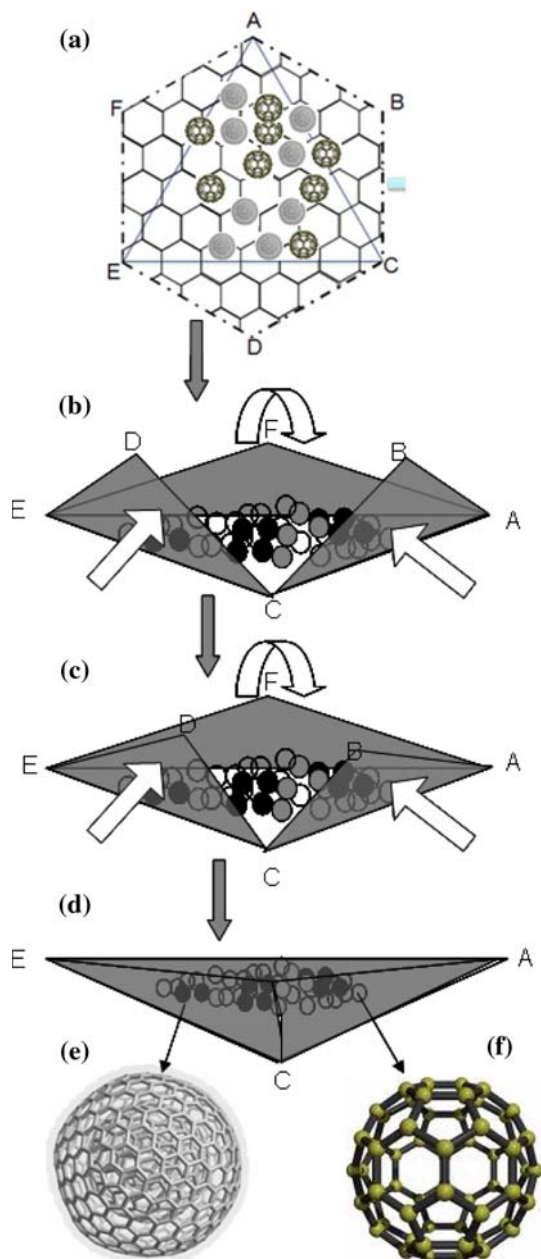

**Fig. 7** A schematic representation of how the triangular envelopes of  $\text{VO}_x$  sheets form **a** a hexagonally packed layer of  $\text{V}_2\text{O}_5/\text{VO}_2$  with some QDs of same material scattered randomly on it **b** the layer folds along zigzag AE, armchair EC and armchair AC of triangle AEC **c** the folding of triangular flaps ABC, CDE and EDF progresses until **d** the triangular envelop AEC is formed. The enveloped spherical particles are either **e** multi-walled  $\text{V}_2\text{O}_5/\text{VO}_2$  fullerenes or **f** single walled  $\text{V}_2\text{O}_5/\text{VO}_2$  fullerenes

on itself from a hexagon, through intermediate stages, into a triangular envelope. The foldings are along arm-chair structure on two sides of the triangle AEC (sides AC and EC in Fig. 7 (a)) and along a zig-zag structure on the third side of the triangle (side AE).

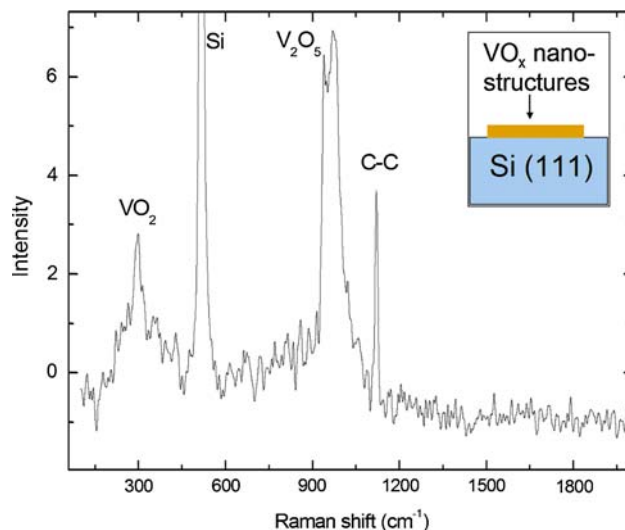


**Fig. 8** Raman spectrum of the  $\text{VO}_2/\text{V}_2\text{O}_5$  triangular capsules containing  $\text{VO}_2/\text{V}_2\text{O}_5$  fullerenes and quantum dots showing a strong peak at  $1,120\text{ cm}^{-1}$  which suggests C–C intercalation of the  $\text{VO}_2/\text{V}_2\text{O}_5$  structure

Raman spectroscopy of these structures (shown in Fig. 8) supports the fact that there exists mixed valence of  $\text{V}^{4+}$  (signified by the  $300\text{ cm}^{-1}$  phonon which is an undertone of the main  $600\text{ cm}^{-1}$  peak which in these samples is masked by the strong Si–Si background noise from the substrate at  $520\text{ cm}^{-1}$ ) and  $\text{V}^{5+}$  from  $930\text{--}970\text{ cm}^{-1}$ . The peak at  $1,120\text{ cm}^{-1}$  suggests the presence of C–C bonds in the  $\text{VO}_2/\text{V}_2\text{O}_5$  structure. As opposed to the carbon modified  $\text{WO}_3$  nano-platelets which showed aromatic carbon apart from C–C bonds, Raman spectroscopy showed no aromatic rings in  $\text{VO}_2/\text{V}_2\text{O}_5$  triangular envelopes.

### Influence of Chlorine on the Conductance of $\text{VO}_x$ Structures

Two samples of the  $\text{VO}_2/\text{V}_2\text{O}_5$  triangular envelopes were produced from laser photolysis of  $\text{VCl}_3$  in ethanol and  $\text{V}_2\text{O}_5$  added to  $\text{VCl}_3$  in ethanol were subjected to conductivity tests using a four-point probe technique by employing a Keithley Semiconductor Characterisation System (Fig. 9). Pure  $\text{V}_2\text{O}_5$  powder shows negligible conductance (inset of Fig. 9) which is enhanced by performing laser photolysis in the presence of  $\text{VCl}_3$  in ethanol. The conductance is highest in the photolysed  $\text{VO}_2/\text{V}_2\text{O}_5$  nanostructures produced from the precursor of  $\text{VCl}_3$  in ethanol. This suggests that in the first photolysis, we form  $\text{VO}_x$  nanostructures of lower content of Cl than in the second one. Furthermore, the  $\text{VO}_x$  structures are sensitive to the presence of Cl which could indicate that  $\text{VO}_x$

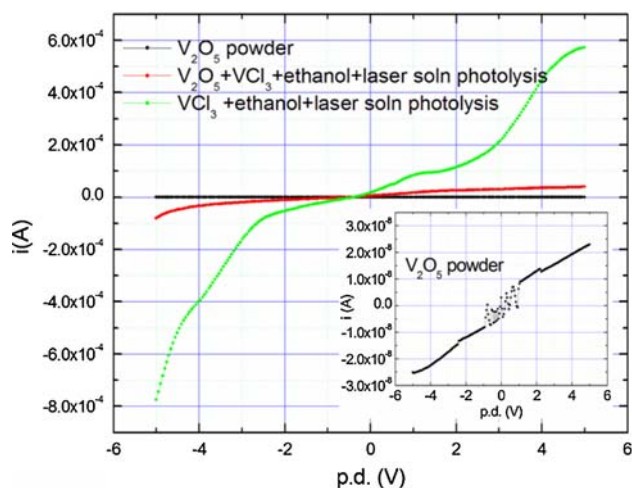


**Fig. 9** The high conductance in photolysed  $\text{VCl}_3$  in ethanol shows the higher sensitivity of  $\text{VO}_2/\text{V}_2\text{O}_5$  triangular envelopes to chlorine exposure compared to ethanol. Inset: the  $i$ - $v$  curve for pure  $\text{V}_2\text{O}_5$  powder

nanostructures are potential chlorine sensors. In both samples, the presence of chlorine shows a more pronounced change than the presence of ethanol.

### Effect of Ethanol on the Conductance of $\text{WO}_x$ Platelets

Two C: $\text{WO}_3$  samples produced by laser solution photolysis were dried for two and three weeks respectively. The sample dried for three weeks was assumed to be more heavily carbon-doped and it only showed slightly more conductivity than the sample dried for two weeks as shown in the inset of Fig. 10. However, exposure of these C: $\text{WO}_3$  nano-platelets to ethanol significantly increased the conductance, confirming that  $\text{WO}_3$  can act as a sensor of ethanol.

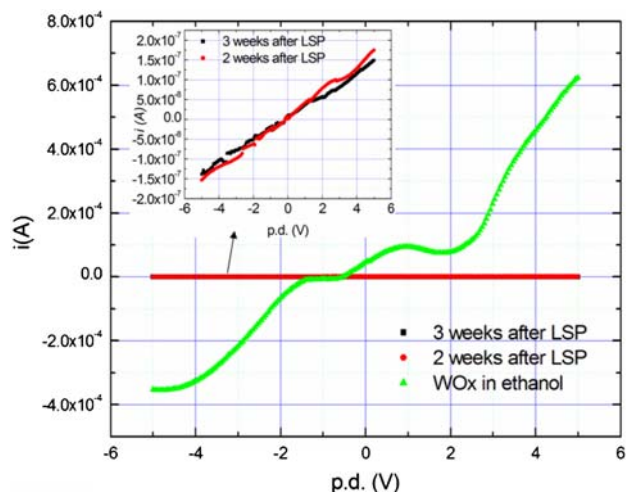

**Fig. 10** The presence of ethanol in the C: $\text{WO}_3$  nano-platelets shows a more pronounced change in conductivity than the presence of carbon

### Conclusion

Production of nano-platelets of carbon modified  $\text{WO}_3$  and 6-nm encapsulated  $\text{VO}_x$  quantum dots by laser solution photolysis have been achieved. Conductivity studies revealed that the  $\text{VO}_2/\text{V}_2\text{O}_5$  nanostructures are more sensitive to atomic C than to the presence of ethanol, whereas the C: $\text{WO}_3$  nano-platelets are more sensitive to ethanol than atomic C.

**Acknowledgments** We acknowledge Nosipho Moloto for her assistance with FIB FEGSEM, Brian Yalisi for the KrF laser and Lerato Shikwambana and Malcolm Govender for the starting materials. Financial and infrastructural support from the CSIR National Laser Centre and characterisation facilitation of the CSIR National Centre for Nano-Structured Materials are acknowledged.

**Open Access** This article is distributed under the terms of the Creative Commons Attribution Noncommercial License which permits any noncommercial use, distribution, and reproduction in any medium, provided the original author(s) and source are credited.

### References

1. F.J. Morin, Phys. Rev. Lett. **3**, 34 (1959)
2. B.W. Faughnan, R.S. Crandall, P.M. Heyman, R.C.A. Review **36**, 177 (1975)
3. B.W. Faughnan, R.S. Crandall, M.A. Lampert, Appl. Phys. Lett. **27**, 275 (1975)
4. C.G. Granqvist, A. Azens, A. Hjelm, L. Kullman, G.A. Niklasson, D. Rönnow, M. Strømme Mattsson, M. Veszeli, G. Vaivars, Sol. Energy **63**, 199–216 (1998)
5. B.W. Mwakikunga, E. Sideras-Haddad, A. Forbes, S.S. Ray, C. Arendse, G. Katumba, in *Metal-to-insulator transitions and the thermochromism of  $\text{VO}_2$  at nanoscale in chromic materials, phenomena and their applications*, ed. by P. Somani (Applied Science Innovations Private Limited (ASIPL), Maharashtra, India, 2009)
6. F. Sediri, N. Gharbi, J. Phys. Chem. Solids **68**, 1821 (2007)
7. B. Li, X. Ni, F. Zhou, J. Cheng, H. Zheng, M. Ji, Solid State Sci. **8**, 1168 (2006)
8. X.-W. Chen, Z. Zhu, M. Havecker, D.S. Su, R. Schlogl, Mater. Res. Bull. **42**, 354 (2007)
9. P. Tägtström, U. Jansson, Thin Solid Films **352**, 107 (1999)
10. J. Yan, W. Huang, Y. Zhang, X. Liu, M. Tu, Physica Status Solidi (A) Appl. Mater. **205**(10), 2409–2412 (2008)
11. L.A. Gea, L.A. Boatner, Appl. Phys. Lett. **68**(22), 3081–3083 (1996)
12. A.H. Mahan, P.A. Parilla, K.M. Jones, A.C. Dillon, Chem. Phys. Lett. **413**, 88 (2005)
13. T. Ben-Messaoud, G. Landry, J.P. Gariépy, B. Ramamoorthy, P.V. Ashrit, A. Haché, Opt. Commun. **281**(24), 6024–6027 (2008)
14. B.W. Mwakikunga, E. Sideras-Haddad, M. Maaza, Optical Mater. **29**(5), 481 (2007)
15. B.W. Mwakikunga, E. Sideras-Haddad, M. Witcomb, C. Arendse, A. Forbes, J. Nanosci. Nanotechnol. **9**, 3286 (2008)
16. B.W. Mwakikunga, A. Forbes, E. Sideras-Haddad, C. Arendse, Phys. Stat. Solidi (a) **205**, 150 (2008)
17. B.W. Mwakikunga, E. Sideras-Haddad, C. Arendse, A. Forbes, Oatube Nanotechnol. **2**, 109 (2009) <http://www.oatube.org/2009/01/bmwakikunga.html>



18. B.W. Mwakikunga, E. Sideras-Haddad, C. Arendse, A. Forbes, P. C. Eklund, T. Malwela, T.K. Hillie, S. Sinha-Ray, *Nano Lett* (2009) (submitted)
19. J. Liu, H. Xia, D. Xue, L. Lu, *J. Am. Chem. Soc.* **131**, 12086 (2009)
20. S. Rajagopal, D. Nataraj, D. Mangalaraj, Y. Djaoued, J. Robichaud, O.Yu. Khyzhun, *Nanoscale Res. Lett.* **4**, 1335 (2009)
21. J. Rajeswari, P.S. Kishore, B. Viswanathan, T.K. Varadarajan, *Nanoscale Res. Lett.* **2**, 496 (2007)
22. X.P. Wang, B.Q. Yang, H.X. Zhang, P.X. Feng, *Nanoscale Res. Lett.* **2**, 405 (2007)
23. B.W. Mwakikunga, A. Forbes, E. Sideras-Haddad, R.M. Erasmus, G. Katumba, B. Masina, *Int. J. Nanoparticles* **1**, 3 (2008)
24. B.W. Mwakikunga, A. Forbes, E. Sideras-Haddad, C. Arendse, *Nanoscale Res. Lett.* **3**, 372 (2008)
25. M. Watanabe, H. Takamura, H. Sugai, *Nanoscale Res. Lett.* **4**, 565 (2009)
26. H. Hada, Y. Yonezawa, A. Yoshida, A. Kurakake, *J. Phys. Chem.* **80**, 2728 (1976)
27. K. Kurihara, J. Kizling, P. Stenius, J.H. Fendler, *J. Am. Chem. Soc.* **105**, 2574 (1983)
28. L. Bronstein, D. Chernshov, P. Valetsky, N. Tkachenko, H. Lemmetyinen, J. Hartmann, S. Forster, *Langmuir* **15**, 83 (1999)
29. J.A. Powell, S.R. Logan, *J. Photochem.* **3**, 189 (1974)
30. J. Pola, M. Marysko, V. Vorlicek, S. Bakardjieva, J. Subrt, Z. Bastl, A. Ouchi, *J. Photochem. Photobiol. Chem.* **199**, 156 (2008)
31. C. Liang, Y. Shimizu, M. Masuda, T. Sasaki, N. Koshizaki, *Chem. Mater.* **16**, 963 (2004)
32. Y. Ishikawa, K. Kawaguchi, Y. Shimizu, T. Sasaki, N. Koshizaki, *Chem. Phys. Lett.* **428**, 426 (2006)
33. J. Livage, *Chem. Mater.* **3**, 578 (1991)
34. A. Picard, I. Daniel, G. Montagnac, P. Oger, *Extremophiles* **11**, 445 (2007)
35. A.C. Ferrari, J. Robertson, *Phys. Rev. B* **64**, 075414 (2001)
36. R. Tenne, I. Margulis, M. Genut, G. Hodes, *Nature* **360**, 444 (1992)
37. J. Liu, D. Xue, *Adv. Mater.* **20**, 2622 (2008)
38. J. Liu, F. Liu, K. Gao, J. Wu, D. Xue, *J. Mater. Chem.* **19**, 6073 (2009)
39. G.T. Chandrappa, N. Stenou, S. Cassaignon, C. Bauvis, J. Livage, *Catal. Today* **78**, 85 (2003)
40. V.V. Ivanovskaya, A.N. Enyashin, A.A. Sofronov, Y.N. Makurin, N.I. Medvedeva, A.L. Ivanovskii, *Solid State Commun.* **126**, 489 (2003)
41. D. Riou, G. Ferey, *J. Solid State Chem.* **120**, 137 (1995)